

Comment on “New Vortex-Matter Size Effect Observed in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ ”

Y. Kopelevich⁺ and P. Esquinazi^{*}

⁺*Instituto de Física, Unicamp, 13083-970 Campinas, São Paulo, Brasil*

^{*}*Abteilung Supraleitung und Magnetismus, Universität Leipzig, Linnéstr. 5, D-04103 Leipzig, Germany*

The Letter of Wang et al. [1] is related to the recently discovered vanishing of the second magnetization peak (SMP) in high- T_c superconductors reducing the sample size [2–4]. This phenomenon has been interpreted [2–4] in terms of thermomagnetic instability (TMI) effects. The TMI approach has also been adopted by Wang et al. in their previous work [5] on the critical sample size temperature dependence $R_{cr}(T)$ measured in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ (Bi2212) single crystals. In contrast, in the recently published Letter [1] the authors claimed that the $R_{cr}(T)$ obtained for Bi2212 crystals is at odds with the TMI model and proposed an alternative explanation of the results assuming that the SMP vanishes as the sample width (or diameter) becomes smaller than the in-plane vortex correlation length $R_c^{2D}(T) \sim J_c(T)^{-1/2}$, where $J_c(T)$ is the critical current density. We demonstrate below that the authors conclusion is misleading.

First of all, we stress that the authors used criterion for the occurrence of the SMP $R(T) \geq R_c^{2D}(T) \equiv R_{cr}(T)$ contradicts the low-temperature results. Indeed, the SMP in Bi2212 does not occur at temperatures below ~ 15 K...20 K in crystals of mm size, i.e. with $R \gg R_{cr}(T)$ (see [3] and refs. therein).

Next, the reported $R_{cr}(T)$ [1] agrees very well with the TMI scenario. Figure 1(a) shows the $R_{cr}(T)$ data from [1]. The solid line in Fig.1(a) is obtained from the equation for the critical sample size according to the TMI theory [6]

$$R_{cr} \simeq (-100\pi C(T)/16J_c(T)\partial J_c/\partial T)^{1/2}, \quad (1)$$

where we assumed for the specific heat $C \propto T^3$ and $J_c(T) \propto \exp(-T/T_0)$ [1]. As Fig. 1(a) demonstrates Eq. (1) fits nicely the experimental data. For a quantitative comparison precise knowledge of $C(T)$ and $J_c(T)$ for the measured samples is required.

Moreover, $R_{cr}(T)$ obtained for Bi2212 [1] is similar to that reported for Nb films [7], where it has unambiguously been demonstrated that $R_{cr}(T)$ separates the adiabatic and isothermal critical states. This similarity is illustrated in Fig.1(b) where the effective critical sample size $s_{cr} = (wd/2)^{1/2}$ [2–4] is plotted vs. T/T_c for both superconductors, with w and d being the sample width (or diameter) and thickness.

In [3] we argued that TMI in Bi2212 is triggered by plastic vortex motion which ceases for $T < 15$ K...20 K, providing us a natural explanation for the SMP vanishing at low temperatures. Summarizing, the results reported in [1] are in good agreement with the TMI scenario of the sample-size-dependent SMP in Bi2212 and partially contradict the authors conclusion.

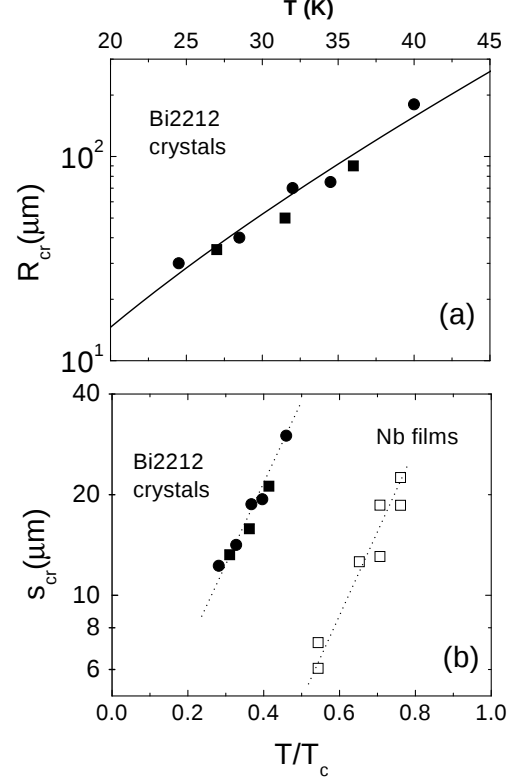


FIG. 1. (a) $R_{cr}(T)$ from [1]. The solid line is obtained from Eq. (1) $R_{cr}(T) = AT^{3/2} \exp(T/T_0)$ with $A = 0.043 \mu\text{m}/\text{K}^{3/2}$ and $T_0 = 15$ K. (b) Effective sample size vs. reduced temperature obtained for Bi2212 crystals [1] ($T_c = 87$ K) and Nb-films [7] ($T_c = 9.2$ K). Dashed lines are only a guide.

-
- [1] Y. M. Wang et al., Phys. Rev. Lett. **86**, 3626 (2001).
 - [2] Y. Kopelevich and P. Esquinazi, J. Low Temp. Phys. **113**, 1 (1998).
 - [3] Y. Kopelevich et al., J. Low Temp. Phys. **116**, 261 (1999).
 - [4] A. Yu. Galkin et al., Solid State Commun. **114**, 1 (2000).
 - [5] Y. M. Wang et al., Physica C **341-348**, 1109 (2000).
 - [6] P. S. Swartz and C. P. Bean, J. Appl. Phys. **39**, 4991 (1968).
 - [7] P. Esquinazi et al., Phys. Rev. B **60**, 12454 (1999).